







Report No. A223036704410100107

Page 1 of 4

Company Name

Shown on Report

SHENZHEN JDB TECH. CO. LTD.

ROOM 1105-1108, NO.2 BUILDING, EST MALL BUSINESS CENTER,

Address NO.698 CHANGBANG ROAD, XIACHENG DISTRICT, 310004,

HANGZHOU, CHINA

The following sample (s) and sample information was/were submitted and identified by/on the behalf of the client

Sample Name 2layers PCB

Material pcb

Sample Received Date Jul. 24, 2023

Testing Period Jul. 24, 2023-Aug.2, 2023

**Test Requested** 

No.	Test Item
1	Decomposition Temperature

**Test Result(s):** Please see the following pages.

Approved by

Annie Lang

Date

Aug. 18, 2023

Annie Lang
Approved Signatory
Approved Signatory
Approved Signatory
Approved Signatory
Approved Signatory
Approved Signatory

No. RDAAD41CF3

Hongwei Industrial Zone, Bao'an 70 District, Shenzhen, Guangdong, China





A223036704410100107 Report No.

Page 2 of 4

## Tested Sample(s)

Sample No.	Sample Name	Material
A2230367044101001	2layers PCB	pcb

### Sample Photo(s)



A2230367044101001





Report No. A223036704410100107

Page 3 of 4

### **Test Item: Decomposition Temperature**

#### 1. Test Equipment

Equipment Name	Model
Thermogravimetric Analysis (TGA)	TG209 F3

#### 2. Environmental Conditions

Temperature: 23.8°C; Humidity: 53% RH

**3. Test Standard:** IPC-TM-650 2.3.40(1995)

#### 4. Test Conditions


(1) Preconditioning: Condition in environment of 23 °C and humidity of 50 %RH for 24h.

(2) Test conditions: Heat from 50°C to 150°C at 5°C/min in N₂ and maintain at 150°C for 15min, then raised from 150°C to 800°C at 5°C/min.

#### 5. Test Result(s)

Test Sample	Decomposition Temperature (°C)
A2230367044101001	331.9 (5% Mass Loss, N <sub>2</sub> )

#### Test Curve:

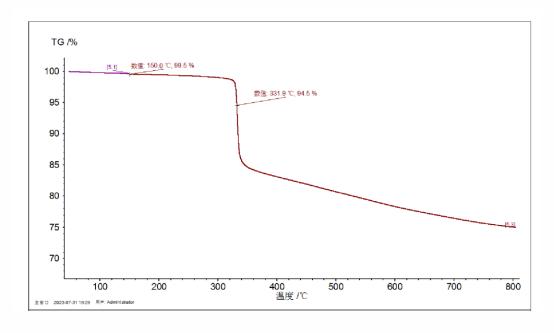



Report No. A223036704410100107

Page 4 of 4

Remark: The testing data and result(s) in this report is(are) just for scientific research, education, internal quality control and product development etc.

#### Statement:

- 1. This report is considered invalid without approved signature, special seal and the seal on the perforation;
- 2.Company Name and Address shown on Report, the sample(s) and sample Information was/were provided by the applicant who should be responsible for the authenticity which CTI hasn't verified;
- 3. The result(s) shown in this report refer(s) only to the sample(s) tested;
- 4. Without written approval of CTI, this report can't be reproduced except in full;
- 5.In case of any discrepancy between the English version and Chinese version of the testing reports(if generated), the Chinese version shall prevail.

\*\*\* End of Report \*\*\*

